

# LAMPIRAN



## **DRAFT ARTIKEL ILMIAH**

# **Porous alumina-hydroxyapatite composites prepared by via protein foaming-consolidation method**

**Ahmad Fadli and Komalasari**

Department of Chemical Engineering, Faculty of Engineering, Riau University

Kampus Binawidya Km 12,5 Simpang Baru Panam, Pekanbaru 28293

fadliunri@yahoo.com

### **Abstract**

In this study, porous alumina-hydroxyapatite (HA) composite bodies were designed for the use in bone implant via protein foaming-consolidation method and the effect of sintering temperature was investigated. Commercial HA powder was used as a bioactive ceramic. Alumina and HA powders were mixed with yolk at an adjusted mass ratio to make slurry. The slurries were cast into cylindrical shaped molds and then dried for foaming and consolidation process. Subsequently, the dried bodies were burned at 600°C for 1 h, followed by sintering at temperatures of 1200, 1350, 1400 and 1550°C for 2 h, respectively. The results show that the sintered bodies were porous with pore size in the range of 20-250 µm and porosity of 42 – 45 %. Increasing sintering temperature from 1200 to 1550°C improved compressive strength from 1 MPa to 8 MPa. TCP phase was found in sintered bodies.

**Keywords:** Porous alumina, Hydroxyapatite, Composites, Protein foaming-consolidation.

## **Introduction**

Implantation of bone by using bone grafts is known strategies for treatment of large bone defects which all lead to limited degree of structural and functional recovery. However, limited supply, donor site morbidity and risk of transmission of pathological organisms impose major limits to their widespread use (Saki et al, 2009). Bone implants become an important thing in the biomedical implant market due to all of the problems arise in the medicine today. To date, several bone substitutes have been approved for clinical applications using a wide range of scaffold materials. In orthopedic applications, a range of bioactive ceramics such as tricalcium phosphate (TCP), hydroxyapatite (HA), bioglass and glass ceramics have been employed because of their excellent bioactivity and bone bonding ability. However, most of them have relatively poor mechanical strength and they cannot meet the requirements for many applications (Kapoor et al, 2010).

Alumina is used to make implantable orthopaedic devices, is a very well tolerated material with minimum tissue reaction after implantation. It exhibits high mechanical strength and minimum wearing. Therefore, it is frequently used in high load-bearing sites such as hip prostheses and dental implants (Saki et al, 2009). No material with both good mechanical and good biological properties exists. However, keeping in mind that bioactivity is more a surface property and mechanical properties are due to the bulk, it is possible to conceive a functionally graded composite deriving its strength from a strong, bio-inert core (like alumina or zirconia) and its bioactivity from a calcium phosphate coating (Gremillard et al, 2006).

The objective of this work is the production of porous alumina-HA composite through protein foaming-consolidation method for potential use as bone substitute. This approach aims to combine the higher strength of the alumina with the biological advantages of the tri calcium phosphate surface, that is, its bioactivity and osteoconduction properties. The effect of sintering temperature on physical and mechanical properties of porous body is investigated.

## **Experimental**

### 2.1 Materials

A commercial alumina powder (Sigma-Aldrich, USA) with a BET specific surface area of 0.39 m<sup>2</sup>/g and an average particle size of 0.25 µm was used as the bioinert ceramic. Commercial HA (Sigma-Aldrich, USA) was used as the bioactive material. Protein used was yolk that freshly isolated from chicken egg (LTK Berhad, Malaysia). Castor oil (Sigma Aldrich, USA) was used as the lubricant for facilitating demolding.

### 2.2 Preparation of porous alumina-HA composite

Protein foaming-consolidation method was used to fabricate porous alumina bodies as reported elsewhere (Fadli and Sopyan, 2009). The slurries were prepared by mixing the alumina, HA powder with yolk in a beaker glass. The slurries were mechanically stirred (Heidolph, RZR 2052 control model) at 150 rpm for 3 h in ambient environment. Subsequently, the slurries were cast in cylindrical open stainless steel mould with 10.75 mm diameter and 15.10 mm height and dried in an air oven (Memmert, 100-800 model) at 180°C for 1 h. Covering the molds with castor oil made demolding easier and led to better surface qualities. Finally, the dried samples were burned in a furnace (Protherm, PLF 160/5 model) at a rate of 10°C min<sup>-1</sup> up to 600°C

for 1 h for removal of the yolk and then sintered at rate of  $2^{\circ}\text{C min}^{-1}$  up to  $1200^{\circ}\text{C}$  -  $1550^{\circ}\text{C}$  for 2 h. Composition of slurries and sintering temperatures studied are as listed in Table 1.

**Table 1** Slurry composition and sintering temperature studied

Slurry	Alumina (g)	HA (g)	Yolk (g)	Sintering temperature ( $^{\circ}\text{C}$ )
S0	24	3.2	24	1200
S1	24	3.2	24	1350
S2	24	3.2	24	1400
S3	24	3.2	24	1550

#### 2.4 Characterization

The particle size of powder was measured using a Nanosizer (Malvern, ZEN1600 model). The apparent density of sintered porous composite samples obtained was measured in an electronic densimeter (Alfa Mirage, MD300S model). The theoretical densities of fully densified alumina,  $3.98\text{ g cm}^{-3}$ , and hydroxyapatite,  $3.14\text{ g cm}^{-3}$ , are used as the references to calculate the total volume fraction of porosity. The crystallinity of the sintered porous samples was analyzed by XRD (Shimadzu, XRD-6000) using Cu Ka radiation at 30 mA, 40 kV. The pore size, interconnection among pores and also the grain structure were examined using FESEM (JEOL, JSM 6700 F model). The mechanical strength of the porous alumina-HA bodies was measured using a universal testing machine (Lloyd, LR10K plus model) by diametrical compression at a loading rate of  $2.5\text{ mm min}^{-1}$  on the samples of 8 mm diameter and


10 mm height. Five scaffolds were used to determine the average value of each compressive test.

## **Results and Discussion**


Protein foaming-consolidation method has been employed for the first time to prepare porous alumina (Fadli and Sopyan, 2009). It was found that physical properties of the porous alumina bodies obtained can be controlled by regulating slurry composition and drying process. The alumina bodies after sintering process show good interconnectivity with pore size in the range of 200-1,000  $\mu\text{m}$ . Even proper control processing condition could provide considerably low density porous bodies, such low ( $< 1 \text{ g cm}^{-3}$ ) that they are floatable on water (Sopyan and Fadli, 2012). Such properties, combined with high mechanical strength, make the porous alumina potential to be a candidate for floating microcarrier application, especially in a bioreactor cell culture.

## **CHARACTERIZATION OF HA POWDER**

Powder of commercial HA revealed flat structure in shape and the particles tend to scatter with size in the range of 100-600 nm (Figure 1a). The average particle size of commercial HA powder was found to be of 765 nm as shown in Fig. 1b. The size of particles will effect on stability and flowability of slurries, leading to variation in porosity and mechanical strength of materials.

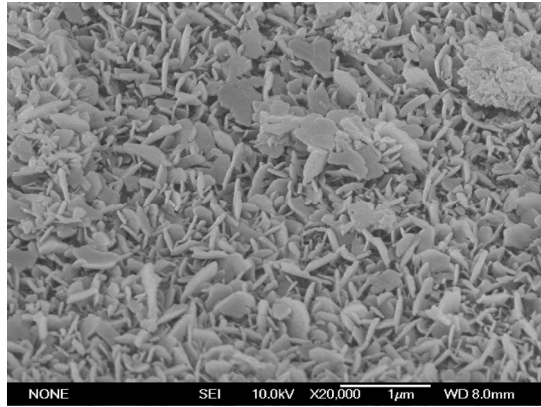


(a)

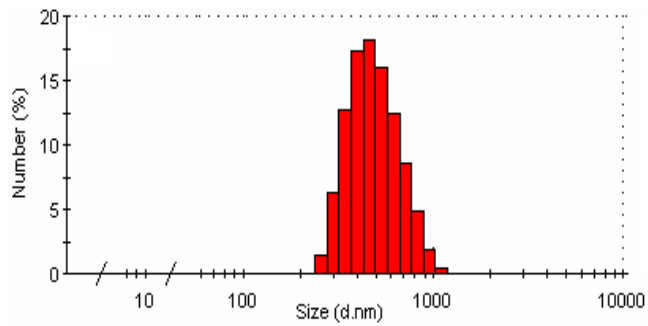

(b)

**Figure 1.** (a) Morphology and (b) Particle size distribution graph of commercial HA powder

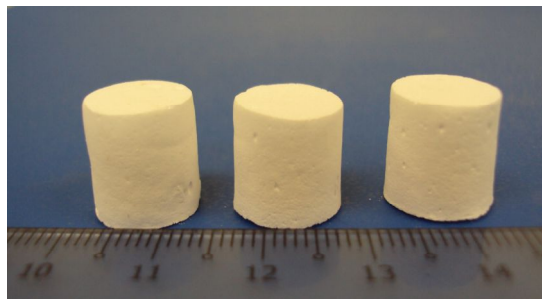

**Figure 2.** Porous alumina-HA composites with cylindrical shape.

Figure 2 shows a photograph three sintered porous alumina-HA composites with cylindrical shapes. The bodies did not show any cracks during both burn out of pore former and sintering.

### **EFFECT OF SINTERING TEMPERATURE ON PHYSICAL PROPERTIES**

To investigate effect of sintering temperature on the physical properties of porous alumina-HA, samples S0, S1, S2 and S3 were evaluated. Measurement of shrinkage, density, porosity and compressive strength of all the samples are presented in Table 2.

**Table 2** Effect of sintering temperature on shrinkage, density, porosity and compressive strength

Slurry	Shrinkage (Vol.%)	Density (g cm <sup>-3</sup> )	Porosity (%)	Compr. strength (MPa)
S0	24.4	2.3	41.8	0.8
S1	28.6	2.0	48.5	1.8
S2	33.0	2.4	39.0	2.1
S3	43.3	2.2	44.6	7.5



When the sintering temperature increased from 1200 to 1550°C, the shrinkage of porous alumina-HA increased from 24.4 to 43.3%. The shrinkage occurred as the yolks were removed and the particles, which were initially packed loosely,



approached and contacted. The removing yolks left holes in the walls. These holes were the source of void that would move from the centre to the outer surface during sintering, at the same time the particles moved towards the internal surface of bodies. These kind of movements led to the shrinkage of bodies. Therefore the shrinkage became intensive with the increasing sintering temperature.

The influence of sintering temperature on the density and porosity is not clear from Table 2. In fact, at a constant slurry composition, sintering temperatures should not have any effect on the density and porosity. The fluctuation of density and porosity due to temperature sintering effect may be caused by the differences of thickness of alumina, HA or TCP phases in the bodies which produced some minor influence of density and porosity. Any clear trend due sintering temperature could not be elucidated from these experimental data.


Table 2 also reveals that the compressive strength of both porous alumina-HA slowly increased when sintering temperature increased from 1200 to 1400°C. The compressive strength of porous alumina-HA in the temperature range was 0.8 – 2.1 MPa. On the other hand, the compressive strength increased faster when sintering temperature increased from 1400 to 1550°C. Owing to a decrease in porosity with the elevating sintering temperature, the compressive strength is supposed to increase with sintering temperature. An increase in sintering temperature led to the higher strength but also reduced the overall porosity. The maximum compressive strength values for porous alumina-HA bodies were 7.5 and 10.6 MPa and achieved at sintering temperature of 1550°C.

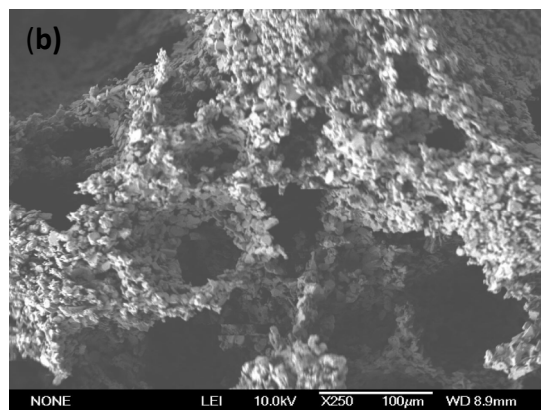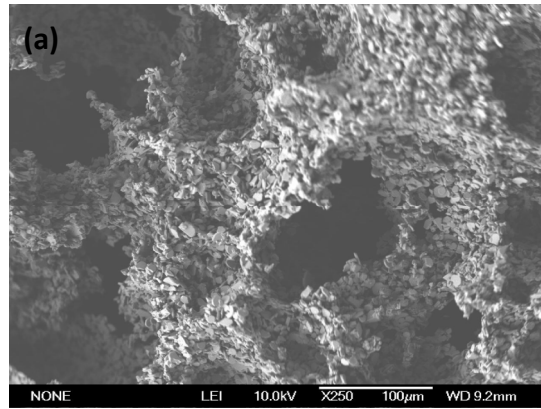


**Figure 3.** Macro structures of bodies after sintered at (a) 1350 and (b) 1550°C

The micro and macrostructure of samples changed obviously with the increasing sintering temperature. Figure 3 shows the surface morphology of the porous alumina-HA samples sintered at 1350 (S1) and 1550°C (S4). Pore size in the sintered bodies was in the range of 20-250  $\mu\text{m}$ . The increased sintering temperature resulted in smaller pore size and denser struts as well as higher interconnectivity of pores (Figure 3b). It is understandable that the shrinkage increased with sintering temperature, thus the pore sizes decreased whereas window size in the pore walls increased.

Figure 4a shows that the particles shape in porous body after 1350°C sintering are irregular. When the sintering temperature increased, the irregular particles enlarged and fused into larger grains. The microstructure of 1550°C sintered sample in Figure 4b shows that HA powder melted and solidly bonded together with alumina particles which led to the enhancement of strength.

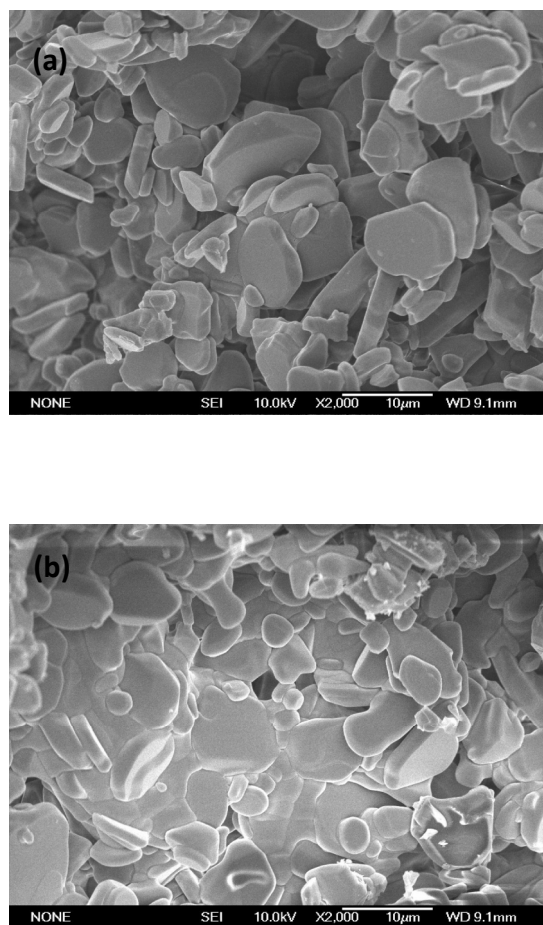

**Figure 4.** Micro structures of bodies after sintered at (a) 1350 and (b) 1550°C.

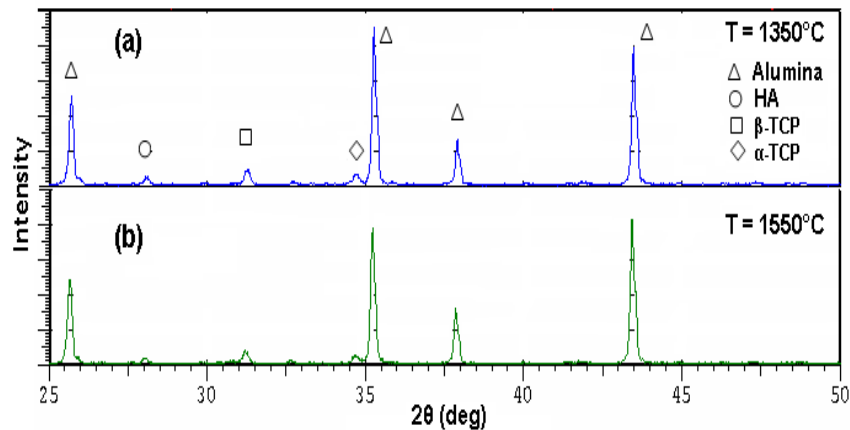

**Figure 5.** XRD pattern of porous alumina-HA bodies after sintered at (a) 1350 and (b) 1550°C

Figure 5 shows XRD patterns of porous alumina-HA sintered at 1350°C (S1) and 1550°C (S4). The crystallinity of HA in the porous alumina-HA sintered at 1550°C was lower than that sintered at 1350°C. The increasing HA peak intensity is believed due to instability of HA at sintering temperatures above 1350°C, and forms decomposed phases such as  $\alpha$ -TCP and  $\beta$ -TCP (Jun et al, 2003). However, Figure 4 reveals that crystallinity of TCP almost did not alter after the samples sintered at 1350 and 1550°C. The alumina phase peaks were constant due to the sintering temperature set was still less than melting point of alumina (i.e 2072°C). Moreover, no additional phase other than alumina, HA and  $\beta$ -TCP identified in the two patterns. This indicates that the sintering process does not alter the composition of the porous composite.

## Conclusion

Porous alumina-HA composite were successfully manufactured via protein foaming-consolidation technique using egg yolk as the foaming agent. The compressive strength of sintered porous alumina-HA obtained by this method was 1 – 8 MPa,

respectively. The sintered porous bodies have open, interconnected porous structure with pore size of 20-250  $\mu\text{m}$ . When the sintering temperatures increased from 1200 to 1550°C, the porous bodies shrunk dramatically leading to the porosity decreasing. The grain size of samples enlarged and fused with the increasing sintering temperature, which lead to the improvement of body strength. XRD results show that crystallinity of porous bodies decreased with the increasing sintering temperatures while the phase of the bodies remains unchanged.

### **Acknowledgmets**

The authors are thankful to the Ministry of National Education, Republic of Indonesia (DIKTI) for Hibah Bersaing Project.

### **References**

- Fadli, A. and I. Sopyan., 2009. “ Preparation of Porous Alumina for Biomedical Applications through Protein Foaming-Consolidation Method”. *Mater. Res. Innovat.* 13(3): 327-329.
- Gremillard, L., Casadei, R., Saiz, E. and A.P. Tomsia., 2006. “Elaboration of self-coating alumina-based porous ceramics”. *J. Mater. Sci.* 41: 5200-5207
- Jun, Y., Kim, W., Kweon, O. and S. Hong., 2003. “The fabrication and biochemical evaluation of alumina reinforced calcium phosphate porous implants”. *Biomaterials*, 24: 3731-3739.
- Kapoor, S. and U. Batra., 2010.” Preparation and Bioactivity Evaluation of Bone like Hydroxyapatite - Bioglass Composite”. *Inter. J. Chem. Bio. Eng.* 3(1): 24-28

- Saki, M., Narbat, M.K., Samadikuchaksaraei, A., Ghafouri, H.B. and F. Gorjipour,. 2009. "Biocompatibility study of a hydroxyapatite-alumina and silicon carbide composite scaffold for bone tissue engineering". *Yakhteh Med. J.* 11(1): 55-60
- Sopyan, I. and A. Fadli,. 2012." Floating porous alumina from protein foaming-consolidation technique for cell culture application". *Ceram. Int.* 38: 5287-5291.

## DAFTAR MAKALAH YANG TELAH DISEMINARKAN

1. **Ahmad Fadli**, Komalasari, 2012, *Fabrication of porous alumina-hydroxyapatite composites via protein foaming-consolidation method: Effect of sintering temperature*, Prosiding Seminar Nasional Teknik Kimia Teknologi Oleo dan Petro Kimia (SNTK TOPI), 11 Juli 2012, Pekanbaru, Riau, Makalah PB 07, hal 124-127.
2. **Ahmad Fadli**, Komalasari, Cory Dian Alfarisi, 2012, *Influence of yolk addition on protein foaming-consolidation porous alumina containing hydroxyapatite nanopowder*, Prosiding Seminar UNRI-UKM ke-7, 10 Oktober 2012, Pekanbaru, Riau.

## SINOPSIS PENELITIAN LANJUTAN (TAHUN 2013)

Bahan keramik seperti alumina berpori dianggap bahan yang atraktif digunakan sebagai tulang implan dan mikrokarir untuk kultur sel. Walaupun alumina memiliki sifat mekanik yang tinggi, akan tetapi alumina bersifat bioinert yang membatasinya untuk diaplikasikan sebagai tulang buatan. Sebaliknya, kalsium phosphate sudah berhasil digunakan untuk mengganti tulang yang rusak karena kalsium phosphat memiliki sifat bioaktif dan biokompatibel dalam pertumbuhan sel-sel tulang. Tujuan penelitian ini adalah membuat komposit alumina-kalsium phosphat berpori untuk aplikasi biomedik menggunakan metode *protein foaming-consolidation*. Strategi ini bertujuan mengkombinasikan sifat mekanik alumina yang tinggi dengan sifat bioaktif dari kalsium phosphat. Penelitian ini direncanakan dua tahun. Pada tahun pertama adalah membuat komposit alumina-kalsium phosphat menggunakan bahan hidroxyapatit komersial, sedangkan pada tahun kedua membuat komposit alumina-kalsium phosphat berpori menggunakan hidroksiapatit yang diperoleh dari metode sol-gel. Pengujian biokompatibiliti komposit yang dilakukan secara *invitro* menggunakan kultur sel. Slurry dibuat dengan mencampurkan alumina dan hidroksiapatit dengan kuning telur, starch dan dispersan. Kemudian slurry dituangkan di dalam mold yang berbentuk silinder dan dikeringkan pada temperatur 180°C selama 1 jam. Green bodi yang diperoleh selanjutnya dibakar dan disinter pada temperatur 1200-1550°C. Pada penelitian ini akan dipelajari pengaruh komposisi slurry, jenis hidroksiapatit dan kondisi proses terhadap viskositi, kemampuan pengembangan dan sifat fisika, mekanik dan kimia komposit yang dibuat.



## BIODATA KETUA PENELITI

Nama : Ahmad Fadli, ST, MT  
Tempat, Tgl lahir : Muara Enim, 25 Oktober 1973  
Pekerjaan : Dosen Universitas Riau  
Alamat kantor : Jurusan Teknik Kimia Fakultas Teknik Universitas Riau  
Kampus Bina Widya Km. 12.5 Panam Pekanbaru Riau 28293  
Alamat rumah : Perum. Taman Duta Mas Blok C3 No. 5 Pekanbaru Riau  
Telp./Fax. : 0761-566937  
Email : [fadliunri@yahoo.com](mailto:fadliunri@yahoo.com)

### Riwayat Pendidikan

Nama PT	Lokasi	Gelar	Tahun tamat	Bidang studi
Universitas Sriwijaya	Palembang	ST	1996	Teknik Kimia
Univ. Gadjah Mada	Yogyakarta	MT	2001	Teknik Kimia

### Riwayat Penelitian

Tahun	Judul Penelitian	Posisi
2008	Pembuatan alumina berpori dengan metode <i>protein foaming-consolidation</i>	Anggota
2005	Pembuatan Pigmen Titanium Dioksida (TiO <sub>2</sub> ) dari Ilmenit (Dibiayai DIKTI, Hibah Bersaing)	Ketua Peneliti
2005	Kristalisasi TiO(OH) <sub>2</sub> dari Titanyl Sulfat pada pembuatan TiO <sub>2</sub> dari ilmenit (Dibiayai oleh DIKTI, Proyek HEDS)	Ketua Peneliti
2005	Adsorpsi Pb <sup>2+</sup> menggunakan kaolin (Dibiayai oleh Universitas Riau)	Anggota
2004	Model kesetimbangan adsorpsi Zn <sup>2+</sup> menggunakan Kaolin (Dibiayai oleh DIKTI, Proyek HEDS)	Anggota
2003	Adsorpsi Pb <sup>2+</sup> menggunakan bentonit (Dibiayai oleh Universitas Riau)	Ketua Peneliti

Publikasi yang terkait dengan penelitian yang diajukan

### Jurnal internasional

1. Ahmad Fadli, Iis Sopyan (2009) Preparation of porous alumina for biomedical applications through protein foaming-consolidation method, *Materials Research Innovations*, Vol. 13 [3], 327-329 (Impact Factor = 0.638)
2. Ahmad Fadli, Iis Sopyan, Maizirwan Mel, Zuraida Ahmad (2011), Porous alumina through protein foaming-consolidation method: effect of dispersant concentration on the physical properties, *Asia-Pacific Journal of Chemical Engineering*, DOI 10.1002/apj.526, In Press. (Impact Factor = 0.583).
3. Ahmad Fadli, Iis Sopyan (2011), Porous ceramics with controllable properties prepared by protein foaming-consolidation method, *Journal of Porous Materials*, 18, 195-203 (Impact Factor = 0.984).
4. Ahmad Fadli, Iis Sopyan (2010), Porous alumina through protein foaming-consolidation method: effect of stirring time and drying temperature on the physical properties, *Advanced Materials Research*, Vol. 93-94, 397-400, Scopus indexed.

#### **Konferensi internasional**

1. Ahmad Fadli, Iis Sopyan (2009), Porous alumina through protein foaming-consolidation method: effect of stirring time and drying temperature on the physical properties, dipresentasikan di *International Conference on Functionalized and Sensing Materials (FuSem-2009)*, Bangkok (Thailand), 7-9 December 2009.
2. Iis Sopyan, Ahmad Fadli (2008), Porous alumina via protein foaming-consolidation method dipresentasikan di *European Materials Research Society (E-MRS 2008) Fall Meeting*, Warsaw (Poland), 15-19 September 2008.
3. Ahmad Fadli, Iis Sopyan (2008), Preparation of porous alumina for biomedical applications through protein foaming-consolidation method, dipresentasikan di *2<sup>nd</sup> International Conference on Functional Materials and Devices (ICFMD)*, Kuala Lumpur, 16-19 June 2008.

Pekanbaru, 30 Desember 2012  
Ketua peneliti

Ahmad Fadli, ST, MT

## BIODATA ANGGOTA PENELITI

Nama : Komalasari, ST., MT  
 NIP/NIK : 19710114 199803 2 001  
 Tempat/Tgl. Lahir : Palembang/ 14 Januari 1971  
 Jenis Kelamin : Perempuan  
 Agama : Islam  
 Golongan : III-a  
 Jabatan Fungsional : Asisten Ahli  
 Perguruan Tinggi : Universitas Riau  
 Alamat Rumah : Jln. Nuri no. 5 Sp. Panam Pekanbaru Riau 28293  
  
 HP : 081365327330  
 Telp/Fax : (62)-761-566937  
 E-mail : [komalaunri@yahoo.com](mailto:komalaunri@yahoo.com)

RIWAYAT PENDIDIKAN PERGURUAN TINGGI			
Tahun Lulus	Program Pendidikan	Perguruan Tinggi	Jurusan/Program Studi
1995	S1	Universitas Sriwijaya	Teknik Kimia
2001	S2	Institut Teknologi Sepuluh Nopember	Teknik Kimia

PENELITIAN dan PUBLIKASI	
1	Elvi Yenie, <b>Komalasari</b> , "Pembuatan Kompos dari Sampah Sayuran : Parameter Suhu dan Waktu Pembalikan", Prosiding Seminar Nasional Teknik Kimia teknologi Oleo dan Petrokimia Indonesia, Universitas Riau, Indonesia (2011)
2	Padil, Sunarno, <b>Komalasari</b> , Yoppy Widyandra, "Pirolisis Cangkang Sawit Menjadi Asap cair dengan Katalis Bentonit : Variabel Waktu Pirolisis dan Rasio Katalis/Cangkang Sawit", Prosiding Seminar Nasional Teknik Kimia teknologi Oleo dan Petrokimia Indonesia, Universitas Riau, Indonesia (2011)
3	Fadli A, <b>Komalasari</b> , Mulia, SA and Debby, RS, "Kesetimbangan Adsorpsi Larutan Zn <sup>2+</sup> pada Kaolin, Jurnal REAKTOR, Universitas Diponegoro, Indonesia (2004).
4	Fadli A, <b>Komalasari</b> , Mulia, SA and Debby, RS, "Adsorpsi Larutan Zn <sup>2+</sup> pada Kaolin, Prosiding Seminar Nasional Teknologi dan Proses Kimia, Universitas Perjuangan Veteran, (2003).
5	<b>Komalasari</b> , and Ismail T, "Sintesa Sodium Sianat dengan Proses Kering", Prosiding Seminar Nasional Fundamental dan Aplikasi Teknik Kimia, Institut Teknologi Sepuluh Nopember (ITS), (2002)
6	<b>Komalasari</b> , Fadli A, "Kinetika Model dari Produksi Titanil Sulfat

	Unreacted Core Model”, Prosiding Seminar Nasional Fundamental dan Aplikasi Teknik Kimia, Institut Teknologi Sepuluh Nopember (ITS), (2002)
7	Erna M, Linda R, <b>Komalasari</b> , and Fadli A, “Adsorpsi Fenol pada Tandan Kosong sawit: Waktu Kontak dan Efek Temperatur”, Prosiding Seminar Nasional Fundamental dan Aplikasi Teknik Kimia, Institut Teknologi Sepuluh Nopember (ITS), (2002)
8	Erna M, Linda R, <b>Komalasari</b> , and Fadli A, “Adsorpsi Fenol pada Tandan Kosong Sawit”, Prosiding Seminar Nasional Teknologi Proses Kimia, Universitas Sumatera Utara, Indonesia (2002).
9	<b>Komalasari</b> , and Ismail T, “Sintesa Sodium Sianat, Pengaruh Waktu Reaksi dan Temperatur”, Prosiding Seminar Nasional Teknologi dan Proses Kimia, , Universitas Perjuangan Veteran, (2001)
10	<b>Komalasari</b> , “Proteksi Katodik Metode Anoda Tumbal”, Prosiding Seminar Nasional Fundamental dan Aplikasi Teknik Kimia, Institut Teknologi Sepuluh Nopember (ITS), (1999)

Pekanbaru, 30 Desember 2012

Komalasari, ST., MT